

Antibacterial Activity of Polyaniline Coated Silver Nanoparticles Synthesized from *Piper Betle* Leaves Extract

Md. Mamun Or Rashid^{a*}, Md. Shafiu Islam^b, Md. Azizul Haque^b, Md. Arifur Rahman^c,
Md. Tanvir Hossain^b and Md. Abdul Hamid^a

^aDepartment of Pharmacy, Noakhali Science and Technology University, Sonapur, Noakhali-3814, Bangladesh. ^bDepartment of Applied Chemistry and Chemical Engineering, Noakhali Science and Technology University, Sonapur, Noakhali-3814, Bangladesh. ^cDepartment of Microbiology, Noakhali Science and Technology University, Sonapur, Noakhali-3814, Bangladesh.

Abstract

Plants or natural resources have been found to be a good alternative method for nanoparticles synthesis. In this study, polyaniline coated silver nanoparticles (AgNPs) synthesized from *Piper betle* leaves extract were investigated for their antibacterial activity. Silver nanoparticles were prepared from the reduction of silver nitrate and NaBH₄ was used as reducing agent. Silver nanoparticles and extracts were mixed thoroughly and then coated by polyaniline. Prepared nanoparticles were characterized by Visual inspection, Ultraviolet-visible spectroscopy (UV), Fourier transform infrared Spectroscopy (FT-IR), Transmission Electron Microscopy (TEM) techniques. Antibacterial activities of the synthesized silver nanoparticles were tested against *Staphylococcus aureus* ATCC 25923, *Salmonella typhi* ATCC 14028, *Escherichia coli* ATCC 25922 and *Pseudomonas aeruginosa* ATCC 27853. UV-Vis spectrum of reaction mixture showed strong absorption peak with centering at 400 nm. The FT-IR results imply that Ag-NPs were successfully synthesized and capped with bio-compounds present in *P. betle*. TEM image showed that Ag-NPs formed were well dispersed with a spherical structures and particle size ranging from 10 to 30 nm. The result revealed that Ag-Extract NPs showed 32.78±0.64 mm zone of inhibition against *S. aureus*, whereas norfloxacin (positive control) showed maximum 32.15±0.40 mm zone of inhibition for *S. aureus*. Again, maximum zone of inhibition 29.55±0.45 mm was found for *S. typhi*, 27.12±0.38 mm for *E. coli* and 21.95±0.45 mm for *P. aeruginosa*. The results obtained by this study can't be directly extrapolated to human; so further studies should be undertaken to established the strong antimicrobial activity of Ag-Extract NPs for drug development program.

Keywords: Silver Nanoparticles; Ag-Extract nanoparticles; *Piper betle*; Antibacterial activity; Zone of inhibition.

Introduction

Nanotechnology deals with the production and stabilization of various types of nanoparticles

(1). Plants or natural resources have been found to be a good alternative method for nanoparticles synthesis, since this method does not use any toxic chemicals and does not require the use of high pressure, energy, and temperature. This green chemistry process has numerous benefits, including environmental friendliness, cost-

* Corresponding author:

E-mail: mamundu7084@gmail.com

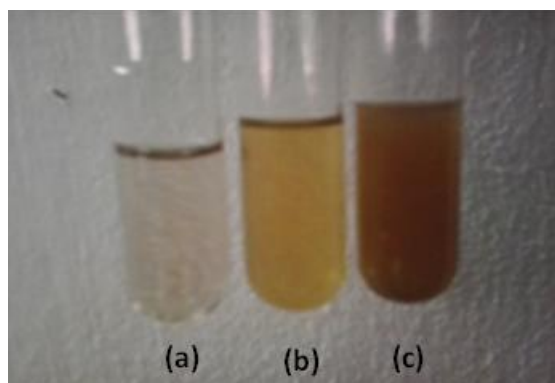


Figure 1. (a)AgNPs solution (b)Aqueous Extract of *P. betle* (c) Ag-Extract NPs

effectiveness, and suitability for pharmaceutical and biomedical applications. At present, several groups of researchers concentrate on biomimetic approaches such as plant or plant leaf extracts, nuts, microorganisms and yeast to synthesize the metal nanoparticles called «green chemical or phytochemical» approach (2-5).

Antibacterial activity of the silver ion has been well established (6) and Ag is currently used to control bacterial growth in a variety of applications, including dental work, catheters, and burn wounds (7,8). In fact, Ag ions and Ag-based compounds are highly toxic to microorganisms, showing strong biocidal effects on as many as 12 species of bacteria including *E. coli* (9). Apart from these antimicrobial activities, Ag-NPs are also known to possess antifungal, anti-inflammatory, antiviral, anti-angiogenesis and antiplatelet properties (10, 11).

The betel (*Piper betle*) is the leaf belonging to the family Piperaceae. The *P. betle* leaves possess antifungal, antiseptic, antihelminthic, antihypertensive etc. medicinal properties (12). Besides, M. Mahfuzul Hoque *et al.*, 2011 claim that ethanolic extract of *P. betle* leaves show antibacterial activity against some food borne pathogens (13).

The aim of this study was to synthesize AgNPs using aqueous leaves extract of *P. betle*, characterized the AgNPs and evaluated the antibacterial activity of Ag-Extract nanoparticles against some Gram positive and Gram negative bacteria.

Experimental

Collection of materials

Fresh young leaves of *P. betle* were

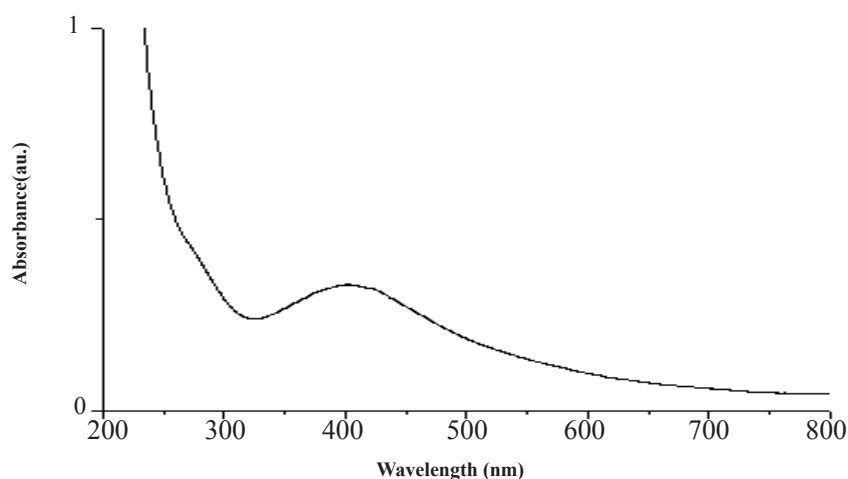


Figure 2. UV-Visible spectrum of AgNPs.

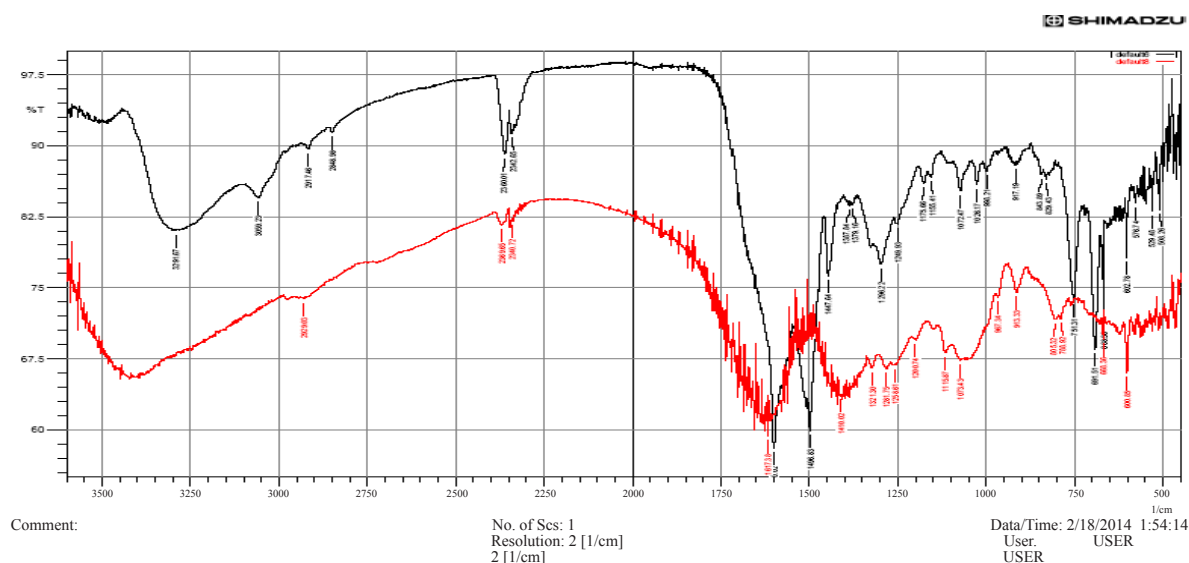


Figure 3. FT-IR spectrum for curve (a) red color- *P. betle* aqueous extract; and curve (b) Ag-Extract nanoparticles.

collected from the local market of Noakhali, Bangladesh. Silver Nitrate (AgNO_3), NaBH_4 and Aniline were collected from the laboratory of Department of Pharmacy, Noakhali Science and Technology University (NSTU).

Preparation of P. betle leaf extract

About 30g of freshly, taxonomically authenticated healthy leaves of *P. betle* were collected in January 2014 from Noakhali district of Bangladesh. *P. betle* leaves extract was

prepared according to K. Gopalakrishnan *et al.*, 2012 (14). The leaves were washed thoroughly with double distilled water, cut into fine pieces and boiled with 150 mL double distilled water for 8-10 min. The extract was cooled to room temperature and filtered through Whatman filter paper. Finally, extract of leaves was stored at refrigerator at 4 °c till further use.

Biosynthesis of silver nanoparticles

Ag nanoparticles were made according to

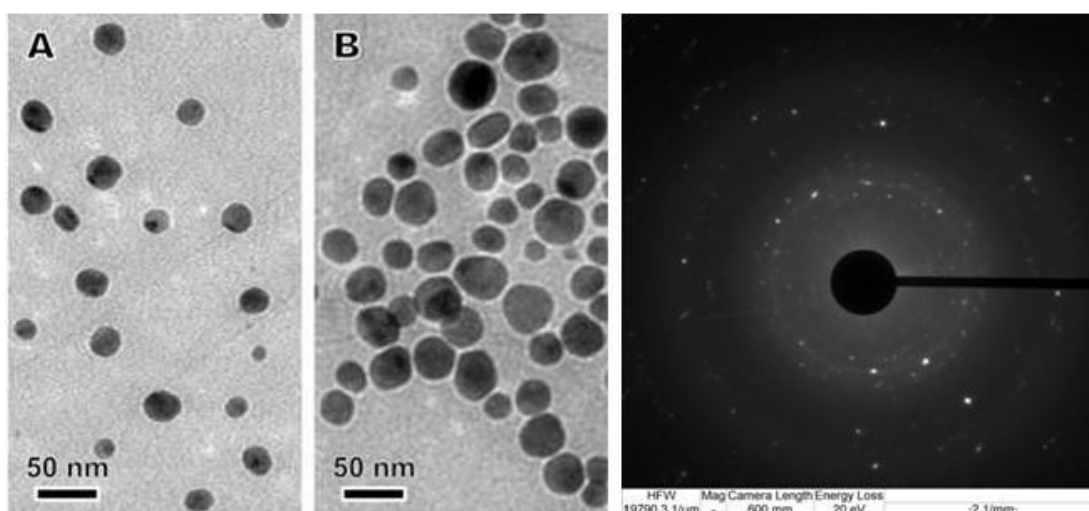


Figure 4. TEM image of bio functionalized AgNPs.

Table 1. Antibacterial activity of *P. betle* formed Ag-NPs on *S. aureus* ATCC 25923, *E. coli* ATCC 25922, *S. typhi* ATCC 14028, *P. aeruginosa* ATCC 27853.

Items	Zone of inhibition (mm)			
	<i>S. aureus</i> ATCC 25923	<i>S. typhi</i> ATCC 14028	<i>E. coli</i> ATCC 25922	<i>P. aeruginosa</i> ATCC 27853
<i>P. betle</i> aqueous leave extract	-	-	-	11.14±0.78
AgNPs	-	-	-	-
Uncoated <i>P. betle</i> loaded AgNPs	-	-	-	-
Coated <i>P. betle</i> loaded AgNPs	32.78±0.64	29.55±0.45	27.12±0.38	21.95±0.55
Norfloracin (control)	22.15±0.40	21.40±0.40	19.23±0.40	17.62±0.40

* Values are the mean of three replicates ± SD (standard error).

the recipe described in the literature (Creighton, 1979; Suh JS *et al.*; 1983) (15, 16). Briefly, a 100-mL aqueous solution of 1.0×10^{-3} M silver nitrate was mixed with a 300-mL aqueous solution of 2.0×10^{-3} M sodium borohydride. Triply distilled water was used for solutions, and both solutions were chilled to ice temperature before mixing. By mixing both solutions, Ag ions were reduced and clustered together to form monodispersed nanoparticles as a transparent solution in aqueous medium. The Ag solution was turned yellow color during mixing. The solution was stirred repeatedly whenever some dark color appeared for approximately an hour until it became stabilized. At this point this solution of Ag nanoparticles was so stable that it did not change color for as long as several months without any stabilizing agent. Because the particle concentration of the solution is only 3.3 nM, it was concentrated 10 times using a rotary vacuum evaporator.

Preparation of Ag-Extracts Nanoparticles

These above two solutions were mixed continuously for 30 min by magnetic stirrer and then stood for 2 h. After that uncoated Ag-extract nanoparticles were prepared.

Coating of Ag-Extract Nanoparticles with Polyaniline

Coating on the Extract-AgNPs were done according to the K. Gopalakrishnan, 2012 (14). 2.7g aniline was dissolved into 300 mL deionized water. After that 68 mL (6 %) of H_2O_2

was added slowly at room temperature. This addition process was completed within 30 min. The reaction was carried out for 23 h at constant stirring rate. The final product was filtered, washed with distilled water and then dried at room temperature. Finally, samples were ready for further analysis (Antimicrobial activity).

Characterization Studies

The formations of silver nanoparticles were confirmed through visual assessment. The reaction mixture turned into dark brown color from its initial brownish-yellow color within 20 min of mixing. This color change indicated the formation of silver nanoparticles. The reduction of pure silver ions was monitored by measuring UV-Vis spectra of the reaction mixture. The absorption spectra of the samples were taken 240 to 540 nm using a UV-Vis spectrophotometer (Hitachi, Model U-2800 spectrophotometer). Water was used as the blank. Again, spectrum was recorded in FTIR (IR Prestige-21, Shimadzu) in the range of $4000-500 \text{ cm}^{-1}$ at a resolution of 4 cm^{-1} . TEM observations were carried out on an H-7100 electron microscope (Hitachi, Tokyo, Japan).

Test Microorganisms

Authentic pure cultures of *Staphylococcus aureus* ATCC 25923, *Salmonella typhi* ATCC 14028, *Escherichia coli* ATCC 25922 and *Pseudomonas aeruginosa* ATCC 27853 were obtained from the Department of Microbiology, NSTU, Bangladesh.

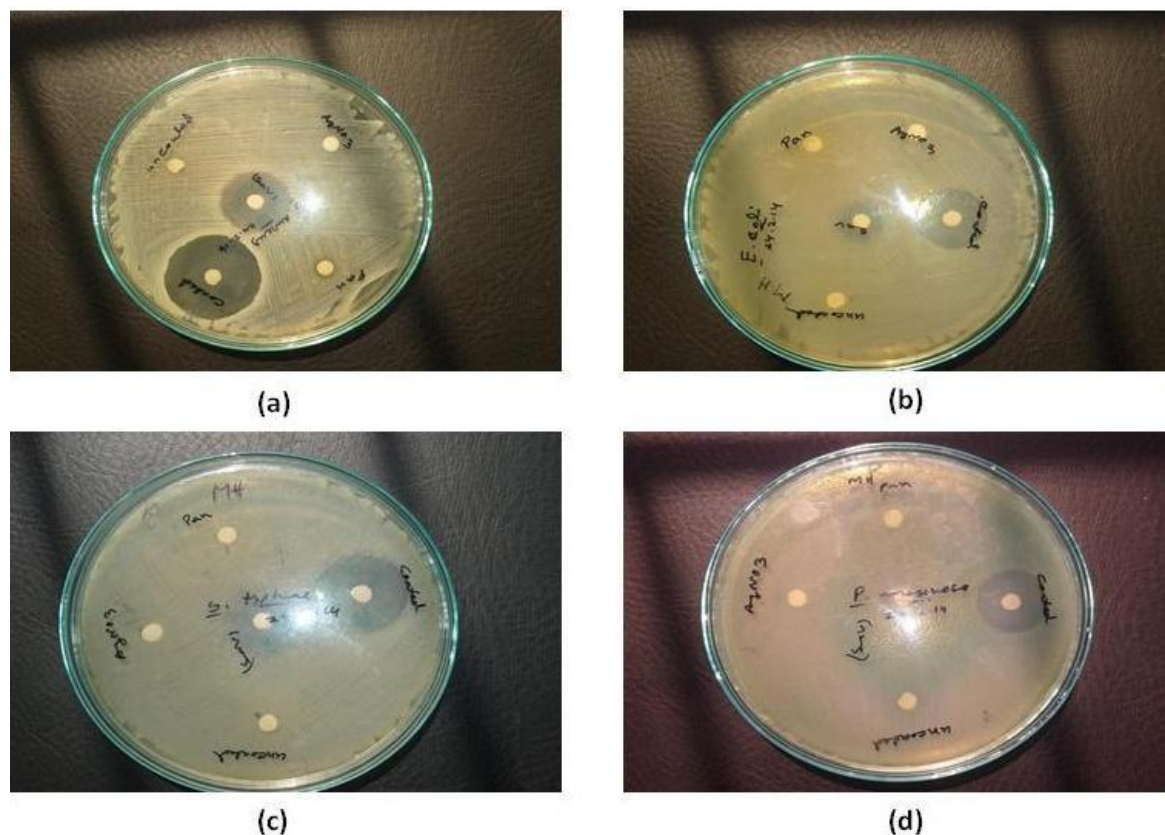


Figure 5. Antibacterial activity of *P. betle* formed Ag-NPs on (a) *S. aureus* ATCC 25923 (b) *E. coli* ATCC 25922 (c) *S. typhi* ATCC 14028 (d) *P. aeruginosa* ATCC 27853

Antimicrobial activity using Kirby-Bauer's Disc diffusion method

Antibacterial activities of the Ag-Extract nanoparticles were determined according to Kirby-Bauer's Disc diffusion method (2006) with slight modifications. The Petri dishes were flooded with Mueller Hinton Agar and after solidification of agar 0.1 mL of diluted inoculums were spread over Mueller Hinton Agar in the dishes using sterile L spreader to achieve confluent growth of test organisms and allowed to dry for 10 min. The sterile readymade discs loaded with *P. betle* extract, AgNPs solution, uncoated AgNPs, coated Ag-Extract NPs. Then they were imposed on the inoculated plates. The plates were then incubated at 37 °C for 36 h. The plates were observed for the zone of inhibition. After incubation at 35 °C for 18 h, the different levels of zone of inhibition were measured. Zone of inhibition was measured using antibiotic zone scale. Norfloxacin was used as positive control.

Result and discussion

Characterization of the synthesized Ag Nanoparticles

Evaluation of Ag-NPs by visual assessment

The formations of silver nanoparticles were confirmed through visual assessment. Within 20 min of the reaction, color of the mixture turned into dark brown from its initial brownish yellow color. This color changing indicated the synthesis of silver nanoparticles (Figure 1). The appearance of dark brown color may be due to the reduction of AgNO_3 (17).

Evaluation of Ag-NPs by UV spectrum

UV-Vis spectrum of reaction mixture at different wavelengths ranging from 300 to 700 nm showed strong absorption peak with centering at approx. 400 nm (Figure 2) indicated the formation of aqueous extract coated Ag-NPs.

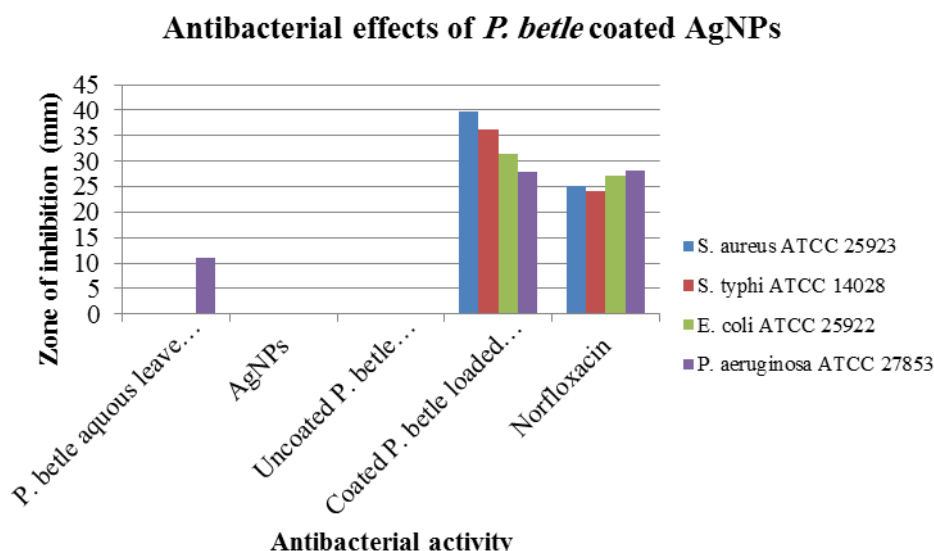


Figure 6. Graphical representation of the antibacterial activity of *P. betle* formed Ag-NPs on *S. aureus* ATCC 25923, *E. coli* ATCC 25922, *S. typhi* ATCC 14028, *P. aeruginosa* ATCC 27853

Evaluation of Ag-NPs through FT-IR spectra

The FT-IR spectra were used to identify the possible biomolecules (including functional group) responsible for the reduction of the Ag⁺ ions and capping of the *P. betle* formed Ag-NPs. Figure 3, showed the FTIR spectra of *P. betle* aqueous extract and bio-synthesized Ag-NPs.

The possible functional groups of leaf extract involved in coating nanoparticle are identified by FTIR analysis. The intense absorption peaks at 3400 cm (curve-a, red color) and 3291.67 cm (curve-b, black color) correspond to N-H stretching of primary amine. The band observed at 3059.23 cm (curve-b) represents =C-H stretching. The weak band observed at 2917.46cm and 2848.98 cm (both in curve-b) indicates the H-C-H asymmetric and symmetric stretching of alkanes. The band observed at 2340.72cm and 2369.65cm (both in curve-a), which are nearly the same band in curve-b, denotes the presence of hydrogen bonded OH stretching of carboxylic acids in leaf extract which may be a reducing/coating agent for silver nanoparticles.

The band at 1617.38 cm (curve-a) and 1600.02 cm (curve-b) represents N-H bending vibration of primary amine. The peak occurs at 1496.83 cm (curve-b) for N-H bending vibration

of sec. amine and at 1447.64cm (curve-b) C-H bending vibration of alkane (CH₃). C-N stretch occurs at 1410.02cm. The band observed at 1387.84 cm and 1379.16 cm (both in curve-b) represent N=O stretching of nitro groups of leaf extract coated on nanoparticles. The arising of functional groups in FTIR spectrum indicates proper coating of leaf extract on silver nanoparticles. The bands at 1296.22, 1249.93, 1175.66, 1155.41 cm (curve-b), which are nearly the same in curve -a, denotes C-H stretching vibration of ester. Beside, C-O stretch occurs at 1072.47, 1026.17 (curve-b) where first is stronger and broader than the second. The band at 843.89, 829.43, 602.78, 668.36 cm shows C-H bending vibration of alkynes. The band at 751.31 cm and 691.51 cm represents the ortho substituted and mono substituted aromatic stretching respectively.

The FT-IR results imply that the Ag-NPs were successfully synthesized and capped with bio-compounds present in the *P. betle* extract by using a green method.

TEM analysis

The TEM image in Figure 4 shows that Ag-NPs were well dispersed with a spherical structures and particle size ranging from 10 to 30

nm with some deviations. Of the total particles, approximately 20 % particles were of 10 nm, 50 % were of 20 nm and remaining 30 % particles were of 30 nm in size.

Assessment of antibacterial activities

The antibacterial activity of the aqueous extracts of *P. betle* leaves were analyzed against both Gram-positive and Gram-negative bacteria, which are presented in (Figure 6, Table 1). After analyzing the above results, it is clear that gram positive bacteria *S. aureus* is more susceptible than other experimental species of gram negative bacteria - *E. coli*, *S. typhi*, *P. aeruginosa*. Maximum zone of inhibition 32.78 ± 0.64 mm was found for *S. aureus*, whereas norfloxacin showed maximum 32.15 ± 0.40 mm zone of inhibition for *S. aureus*. Again, maximum zone of inhibition 29.55 ± 0.45 mm was found for *S. typhi*, 27.12 ± 0.38 mm for *E. coli* and 21.95 ± 0.45 mm for *P. aeruginosa*.

Conclusion

We have demonstrated a good method for developing a simple, safe, cost-effective, and ecofriendly preparation of AgNPs using aqueous extract of *P. betle*. The biosynthesized silver nanoparticles have spherical shapes and the particle size ranges from 10 to 30 nm approximately. The FTIR spectra revealed the involvement of hydroxyl moieties and N-H bonding in the formation of Ag-NPs. They showed potential antibacterial activity against both Gram-positive and Gram negative bacteria. In our study we also found, Gram positive bacteria are more susceptible on Ag-Extract NPs rather than Gram negative bacteria. Application of these synthesized AgNPs based on our findings may lead to valuable discoveries in various fields, including medical devices and in the pharmaceutical and biomedical industries. The results obtained by this study cannot be directly extrapolated to human; further studies should be undertaken to elucidate the exact mechanism of action by which AgNPs-extracts exert their antimicrobial effect which can be used in drug development program for safe health care services.

Acknowledgments

Authors would like to express gratitude to the authority of Noakhali Science and Technology University (NSTU) for their co-operation and suggestion in this research. We are thankful to the Department of Applied Chemistry and Chemical Engineering, NSTU for providing lab facilities during this research.

References

- (1) Feymen R. There's plenty of room at the bottom. *Science* (1991) 254: 1300–1301.
- (2) Savitamma N, Rao ML and Devi PS. Evaluation of antimicrobial efficiency of biologically synthesized silver nanoparticles using stem bark of *Boswellia ovalifoliolata* Bal. and Henry and *Shorea tumbuggaia* Roxb. *J. Biol. Sci.* (2011) 11: 39-45.
- (3) Ramgopal M, Saisushma C, Attitalla IH and Alhasin AM. A facile green synthesis of silver nanoparticles using soap nuts. *Res. J. Microbiol.* (2011) 6: 432-38.
- (4) Sinha S, Pan I, Chanda P and Sen SK. Nanoparticles fabrication using ambient biological resources. *J. Appl. Biosci.* (2009) 19: 1113-30.
- (5) Kannan N and Subbalaxmi S. Green synthesis of silver nanoparticles using *Bacillus subtilis* IA751 and its antimicrobial activity. *Res. J. Nanosci. Nanotechnol.* (2011) 1: 87-94.
- (6) Jung WK, Koo HC, Kim KW, Shin S, Kim SH and Park YH. Antibacterial activity and mechanism of action of the silver ion in *Staphylococcus aureus* and *Escherichia coli*. *Appl. Environ. Microbiol.* (2008) 74: 2171–78.
- (7) Catauro M, Raucci MG, De Gaetano FD and Marotta A. Antibacterial and bioactive silver-containing $\text{Na}_2\text{O} \cdot \text{CaO} \cdot 2\text{SiO}_2$ glass prepared by sol-gel method. *J. Mater. Sci. Mater. Med.* (2004) 15: 831-7.
- (8) Crabtree JH, Burchette RJ, Siddiqi RA, Huen IT, Handott LL and Fishman A. The efficacy of silver-ion implanted catheters in reducing peritoneal dialysis-related infections. *Perit. Dial. Int.* (2003) 23: 368-74.
- (9) Zhao G and Stevens Jr SE. Multiple parameters for the comprehensive evaluation of the susceptibility of *Escherichia coli* to the silver ion. *Biomaterials.* (1998) 11: 27-32.
- (10) Monteiro DR, Silva S, Negri M, Gorup LF, de Camargo ER, Oliveira R, Barbosa DB and Henriques M. Silver nanoparticles: Influence of stabilizing agent and diameter on antifungal activity against *Candida albicans* and *Candida glabrata* biofilms. *Letts. Appl. Microbiol.* (2012) 54: 383–391.
- (11) Martínez-Gutiérrez F, Thi EP, Silverman JM, de Oliveira CC, Svensson SL, Vanden Hoek A, Sánchez EM, Reiner NE, Gaynor EC and Prydzial EL. Antibacterial activity, inflammatory response, coagulation and cytotoxicity effects of silver nanoparticles. *Nanomed.*

- Nonotech. Biol. Med.* (2012) 8: 328–336.
- (12) Evans P, Bowers W and Funk E. Identification of fungicidal and nematocidal components in the leaves of *Piper betle* (Piperaceae). *J. Agric. Food Chem.* (1984) 32: 1254-1256.
- (13) Hoque MM, Rattila S, Shishir MA, Bari ML, Inatsu Y and Kawamoto S. Antibacterial activity of ethanol extract of betel leaf (*Piper betle* L.) against some food borne pathogens. *Bangl. J. Microbiol.* (2011) 28: 58-63.
- (14) Gopalakrishnan K, Ramesh C, Ragunathan V and Thamilselvan M. Antibacterial activity of Cu₂O nanoparticles on E.Coli synthesized from *Tridax Procumbens* leaf extract and surface coating with polyaniline. *Dig. J. Nanomater. Bios.* (2012) 7: 833-839.
- (15) Creighton JA, Blatchford CG and Albrecht MG. Plasma resonance enhancement of Raman scattering by pyridine adsorbed on silver or gold sol particles of size comparable to the excitation wavelength. *J. Chem. Soc.* (1979) 75: 790-8.
- (16) Suh JS, DiLella DP and Moskovits M. Surface-enhanced Raman spectroscopy of colloidal metal systems: a two-dimensional phase equilibrium in *p*-aminobenzoic acid adsorbed on silver. *J. Phys. Chem.* (1983) 87: 1540-4.
- (17) Mulvaney P. Surface plasmon spectroscopy of nanosized metal particles. *Langmuir.* (1996) 12: 788–800.
-
- This article is available online at <http://www.ijpr.ir>